


Centre Scientifique et Technique du Bâtiment

84 avenue Jean Jaurès
CHAMPS-SUR-MARNE
F-77447 Marne-la-Vallée Cedex 2
Tél. : (33) 01 64 68 82 82
Fax : (33) 01 60 05 70 37



CSTB
le futur en construction

MEMBRE DE L'EOTA

European Technical Approval

ETA-11/0354

(English language translation, the original version is in French language)

Nom commercial :

Trade name:

Titulaire :

Holder of approval:

Type générique et utilisation prévue du produit de construction :

Generic type and use of construction product:

Validité du :
au :

Validity from / to:

Usine de fabrication :

Manufacturing plant:

Le présent Agrément technique européen contient :

This European Technical Approval contains:

Injection system Hilti HIT-CT 1

**Hilti Corporation
Feldkircherstrasse 100
FL-9494 Schaan
Principality of Liechtenstein**

Cheville à scellement de type "à injection" pour fixation dans le béton non fissuré M8 à M24, fers à béton 8 à 25mm.

Bonded injection type anchor for use in non cracked concrete: sizes M8 to M24, rebar 8 to 25mm

**27/08/2012
30/09/2016**

Hilti plants

24 pages incluant 14 annexes faisant partie intégrante du document.

24 pages including 14 annexes which form an integral part of the document.

This European Technical Approval replaces ETA-11/0354 with validity from 30/09/2011 to 30/09/2016

Cet Agrément technique Européen remplace l'ETA-11/0354 valide du 30/09/2011 au 30/09/2016



Organisation pour l'Agrément Technique Européen
European Organisation for Technical Approvals

I LEGAL BASES AND GENERAL CONDITIONS

1. This European Technical Approval is issued by the Centre Scientifique et Technique du Bâtiment in accordance with:

- Council Directive 89/106/EEC of 21 December 1988 on the approximation of laws, regulations and administrative provisions of Member States relating to construction products¹, modified by the Council Directive 93/68/EEC of 22 July 1993² and Regulation (EC) N° 1882/2003 of the European Parliament and of the Council³;
- Décret n° 92-647 du 8 juillet 1992⁴ concernant l'aptitude à l'usage des produits de construction;
- Common Procedural Rules for Requesting, Preparing and the Granting of European Technical Approvals set out in the Annex of Commission Decision 94/23/EC⁵;
- Guideline for European Technical Approval of « Metal Anchors for use in Concrete » ETAG 001, edition 1997, Part 1 « Anchors in general » and Part 5 « Bonded anchors ».

2. The Centre Scientifique et Technique du Bâtiment is authorised to check whether the provisions of this European Technical Approval are met. Checking may take place in the manufacturing plant (for example concerning the fulfilment of assumptions made in this European Technical Approval with regard to manufacturing). Nevertheless, the responsibility for the conformity of the products with the European Technical Approval and for their suitability for the intended use remains with the holder of the European Technical Approval.

3. This European Technical Approval is not to be transferred to manufacturers or agents of manufacturer other than those indicated on page 1; or manufacturing plants other than those indicated on page 1 of this European Technical Approval.

4. This European Technical Approval may be withdrawn by the Centre Scientifique et Technique du Bâtiment pursuant to Article 5 (1) of the Council Directive 89/106/EEC.

5. Reproduction of this European Technical Approval including transmission by electronic means shall be in full. However, partial reproduction can be made with the written consent of the Centre Scientifique et Technique du Bâtiment. In this case partial reproduction has to be designated as such. Texts and drawings of advertising brochures shall not contradict or misuse the European Technical Approval.

6. The European Technical Approval is issued by the approval body in its official language. This version corresponds to the version circulated within EOTA. Translations into other languages have to be designated as such.

1 Official Journal of the European Communities n° L 40, 11.2.1989, p. 12

2 Official Journal of the European Communities n° L 220, 30.8.1993, p. 1

3 Official Journal of the European Union L 284, 31 October 2003, p. 25

4 Journal officiel de la République française du 14 juillet 1992

5 Official Journal of the European Communities n° L 17, 20.1.1994, p. 34

II SPECIFIC CONDITIONS OF THE EUROPEAN TECHNICAL APPROVAL

1 Definition of product and intended use

1.1 Definition of product

The injection system Hilti HIT-CT 1 is a bonded anchor system (injection type) consisting of a foil pack with injection mortar Hilti HIT-CT 1 and a steel element.

The steel element can be made of zinc plated carbon (HIT-V), rebar, stainless steel (HIT-V-R), or high corrosion resistant stainless steel (HIT-V-HCR).

The steel element is placed into a rotary/percussion drilled hole filled with the injection mortar and is anchored via the bond between the metal part and concrete.

An illustration of the product is provided in Annex 1 and 2.

1.2 Intended use

The anchor is intended to be used for anchorages for which requirements for mechanical resistance and stability and safety in use in the sense of the Essential Requirements 1 and 4 of Council Directive 89/106/EEC shall be fulfilled and failure of anchorages made with these products would compromise the stability of the works, cause risk to human life and/or lead to considerable economic consequences. Safety in case of fire (Essential Requirement 2) is not covered in this ETA. The anchor is to be used only for anchorages subject to static or quasi-static loading in reinforced or unreinforced normal weight concrete of strength classes C 20/25 at minimum and C50/60 at most according to EN 206-1: 2000-12. It may be anchored in non-cracked concrete only.

The elements made of zinc plated carbon steel (Threaded rods HIT-V) may only be used in concrete subject to dry internal conditions.

The elements made of stainless steel A4 (Threaded rods HIT-V-R) may be used in structures subject to dry internal conditions and also in structures subject to external atmospheric exposure (including industrial and marine environment), or exposure in permanently damp internal conditions, if no particular aggressive conditions exist. Such particular aggressive conditions are e.g. permanent, alternating immersion in seawater or the splash zone of seawater, chloride atmosphere of indoor swimming pools or atmosphere with extreme chemical pollution (e.g. in desulphurization plants or road tunnels where de-icing materials are used).

The elements made of high corrosion resistant stainless steel (HCR) (Threaded rods HIT-V-HCR) may be used in structures subject to dry internal conditions and also in structures subject to external atmospheric exposure, in permanently damp internal conditions or in other particular aggressive conditions. Such particular conditions are e.g. permanent, alternating immersion in seawater or the splash zone of seawater, chloride atmosphere of indoor swimming pools or atmosphere with chemical pollution (e.g. in desulphurization plants or road tunnels where de-icing materials are used).

Elements made of rebar:

Post-installed reinforcing bars may be used as anchor designed in accordance with the EOTA Technical Report TR 029 only. Such applications are e.g. concrete overlay or shear dowel connections or the connections of a wall predominantly loaded by shear and compression forces with the foundation, where the reinforcing bars act as dowels to take up shear forces. Connections with post-installed reinforcing bars in concrete structures designed in accordance with EN1992-1-1: 2004 are not covered by this European technical approval.

The anchor may be installed in dry or wet concrete for all diameters (use category 1).

Installation	Substrate		
	Dry concrete	Wet concrete	Flooded hole
All diameters	Yes	Yes	Not qualified

The anchor may be used in the following temperature ranges:

- Temperature range I: -40 °C to +40 °C
(max long term temperature +24 °C and max short term temperature +40 °C)
- Temperature range II: -40 °C to +80 °C
(max long term temperature +50 °C and max short term temperature +80 °C).

The provisions made in this European Technical Approval are based on an assumed intended working life of the anchor of 50 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

2 Characteristics of product and methods of verification

2.1 Characteristics of product

The steel elements and the mortar foil packs correspond to the drawings and provisions given in Annexes 1 to 2. The characteristic material values, dimensions and tolerances of the anchor not indicated in Annexes 3 to 4 shall correspond to the respective values provided in the technical documentation⁶ of this European Technical Approval. The characteristic anchor values for the design of anchorages are provided in Annexes 10 to 14.

The two components of the Hilti HIT-CT 1 injection mortar are delivered in an unmixed condition in foil packs of sizes 330 ml or 500 ml according to Annex 1. Each foil pack is marked with the identifying, the trade name "Hilti HIT-CT 1", the production date, the production time and expiration date.

Each threaded rod HIT-V is marked with the marking of steel grade, size and length in accordance with Annex 3. Each threaded rod made of stainless steel is marked with the additional letter "R". Each threaded rod made of high corrosion resistant steel is marked with the additional letter "HCR".

Elements made of reinforcing bar shall comply with the specifications given in Annex 4.

Explanations of the markings and the corresponding materials are given in Annexes 3 to 4.

The marking of embedment depth for the steel element threaded rod HIT-V and reinforcing bar may be done on jobsite.

2.2 Methods of verification

The assessment of suitability of the anchor for the intended use in relation to the requirements for mechanical resistance and stability and safety in use in the sense of the Essential Requirements 1 and 4 has been made in accordance with the « Guideline for European Technical Approval of Metal Anchors for use in Concrete », Part 1 « Anchors in general » and Part 5 « Bonded anchors », on the basis of Option 7.

In addition to the specific clauses relating to dangerous substances contained in this European Technical Approval, there may be other requirements applicable to the products falling within its scope (e.g. transposed European legislation and national laws, regulations and administrative provisions). In order to meet the provisions of the UE Construction Products Directive, these requirements need also to be complied with, when and where they apply.

⁶ The technical documentation of this European Technical Approval is deposited at the Centre Scientifique et Technique du Bâtiment and, as far as relevant for the tasks of the approved bodies involved in the attestation of conformity procedure, is handed over to the approved bodies.

3 Evaluation of Conformity and CE marking

3.1 Attestation of conformity system

The system of attestation of conformity 2 (i) (referred to as system 1) according to Council Directive 89/106/EEC Annex III laid down by the European Commission provides:

a) Tasks for the manufacturer:

1. Factory production control,
2. Further testing of samples taken at the factory by the manufacturer in accordance with a prescribed test plan.

b) Tasks for the approved body:

3. Initial type-testing of the product,
4. Initial inspection of factory and of factory production control,
5. Continuous surveillance, assessment and approval of factory production control.

3.2 Responsibilities

3.2.1. Tasks of the manufacturer, factory production control

The manufacturer has a factory production control system in the plant and exercises permanent internal control of production. All the elements, requirements and provisions adopted by the manufacturer are documented in a systematic manner in the form of written policies and procedures. This production control system ensures that the product is in conformity with the European Technical Approval.

The manufacturer shall only use raw materials supplied with the relevant inspection documents as laid down in the prescribed test plan⁷. The incoming raw materials shall be subject to controls and tests by the manufacturer before acceptance. Check of incoming materials such as resin and hardener shall include control of the inspection documents presented by suppliers (comparison with nominal values) by verifying appropriate properties.

The frequency of controls and tests conducted during production is laid down in the prescribed test plan taking account of the automated manufacturing process of the anchor.

The results of factory production control are recorded and evaluated. The records include at least the following information:

- designation of the product, basic material and components;
- type of control or testing;
- date of manufacture of the product and date of testing of the product or basic material and components;
- result of control and testing and, if appropriate, comparison with requirements;
- signature of person responsible for factory production control.

The records shall be presented to the inspection body during the continuous surveillance. On request, they shall be presented to the Centre Scientifique et Technique du Bâtiment.

Details of the extent, nature and frequency of testing and controls to be performed within the factory production control shall correspond to the prescribed test plan which is part of the technical documentation of this European Technical Approval.

3.2.2. Tasks of approved bodies

3.2.2.1. Initial type-testing of the product

For initial type-testing the results of the tests performed as part of the assessment for the European Technical Approval shall be used unless there are changes in the production line or plant. In such cases the necessary initial type-testing has to be agreed between the Centre Scientifique et Technique du Bâtiment and the approved bodies involved.

3.2.2.2. Initial inspection of factory and of factory production control

The approved body shall ascertain that, in accordance with the prescribed test plan, the factory and the factory production control are suitable to ensure continuous and orderly manufacturing of the anchor according to the specifications mentioned in 2.1. as well as to the Annexes to the European Technical Approval.

3.2.2.3. Continuous surveillance

The approved body shall visit the factory at least once a year for regular inspection. It has to be verified that the system of factory production control and the specified automated manufacturing process are maintained taking account of the prescribed test plan.

Continuous surveillance and assessment of factory production control have to be performed according to the prescribed test plan.

The results of product certification and continuous surveillance shall be made available on demand by the certification body or inspection body, respectively, to the Centre Scientifique et Technique du Bâtiment. In cases where the provisions of the European Technical Approval and the prescribed test plan are no longer fulfilled the conformity certificate shall be withdrawn.

3.3 CE-Marking

The CE marking shall be affixed on each packaging of anchors. The symbol « CE » shall be accompanied by the following information:

- identification number of the certification body;
- name or identifying mark of the producer and manufacturing plant;
- the last two digits of the year in which the CE-marking was affixed;
- number of the EC certificate of conformity;
- number of the European Technical Approval;
- number of the European Technical Guideline;
- use category (ETAG 001-5 Option 7);
- size.

4 Assumptions under which the suitability of the product for the intended use was favourably assessed

4.1. Manufacturing

The anchor is manufactured in accordance with the provisions of the European Technical Approval using the automated manufacturing process as identified during inspection of the plant by the Centre Scientifique et Technique du Bâtiment and the approved body and laid down in the technical documentation.

4.2. Installation

4.2.1. Design of anchorages

The suitability of the anchor for the intended use is given under the following conditions:

The anchorages are designed in accordance with the EOTA Technical Report TR 029⁸ "Design of bonded anchors" under the responsibility of an engineer experienced in anchorages and concrete work. Verifiable calculation notes and drawings are prepared taking account of the loads to be anchored. The position of the anchor is indicated on the design drawings (e.g. position of the anchor relative to reinforcement or to supports, etc.).

Post-installed reinforcing bars may be used as anchor designed in accordance with the EOTA Technical Report TR 029 only. The basic assumptions for the design according to anchor theory shall be observed. This includes the consideration of tension and shear loads and the corresponding failure modes as well as the assumption that the base material (concrete structural element) remains essentially in the serviceability limit state (either non-cracked or cracked) when the connection is loaded to failure. Such applications are e.g. concrete overlay or shear dowel connections or the connections of a wall predominantly loaded by shear and compression forces with the foundation, where the rebars act as dowels to take up shear forces. Connections with reinforcing bars in concrete structures designed in accordance with EN1992-1-1: 2004 (e.g. connection of a wall loaded with tension forces in one layer of the reinforcement with the foundation) are not covered by this European technical approval.

4.2.2. Installation of anchors

The suitability for use of the anchor can only be assumed if the anchor is installed as follows:

- anchor installation carried out by appropriately qualified personnel and under the supervision of the person responsible for technical matters on the site;
- use of the anchor only as supplied by the manufacturer without exchanging the components of an anchor;
- commercial standard threaded rods, washers and hexagon nuts may also be used if the following requirements are fulfilled:
 - material, dimensions and mechanical properties of the metal parts according to the specifications given in Annex 5, Table 3,
 - confirmation of material and mechanical properties of the metal parts by inspection certificate 3.1 according to EN 10204:2004, the documents should be stored,
 - marking of the threaded rod with the envisage embedment depth. This may be done by the manufacturer of the rod or the person on jobsite.
- anchor installation in accordance with the manufacturer's specifications and drawings using the tools indicated in the technical documentation of this European Technical Approval;
- checks before placing the anchor to ensure that the strength class of the concrete in which the anchor is to be placed is in the range;
- check of concrete being well compacted, e.g. without significant air voids;
- keeping the effective anchorage depth;

⁸ The Technical Report TR 029 "Design of Bonded Anchors" is published in English on EOTA website www.eota.eu.

- keeping of the edge distance and spacing to the specified values without minus tolerances;
- drilling by hammer-drilling or Hilti hollow drill bit TE-CD/TE-YD;
- positioning of the drill holes without damaging the reinforcement;
- in case of aborted drill hole: the drill hole shall be filled with mortar;
- clean the hole in accordance with Annex 6; before brushing clean the brush and checking whether the brush diameter according to Annex 9 Table 5 is sufficient. The brush shall produce natural resistance as it enters the anchor hole. If this is not the case a new brush or a brush with a larger diameter must be used;
- anchor installation ensuring the specified embedment depth, that is the appropriate depth marking of the anchor not exceeding the concrete surface;
- for overhead installation piston plugs shall be used, embedded metal parts shall be fixed with during the curing time, e.g. with wedges,
- for injection of the mortar in bore holes ≥ 250 mm piston plugs shall be used
- mortar injection by using the equipment including the special mixing nozzle shown in Annex 1; discarding the first portion of mortar of each new cartridge until an homogeneous colour is achieved; taking from the manufacturer instruction the admissible processing time (open time) of a cartridge as a function of the ambient temperature of the concrete; filling the drill hole uniformly from the drill hole bottom, in order to avoid entrapment of air; removing the special mixing nozzle slowly bit by bit during pressing-out; filling the drill hole with a quantity of the injection mortar corresponding to 2/3 of the drill hole; inserting immediately the threaded rod, slowly and with a slight twisting motion, removing excess of injection mortar around the rod; observing the curing time according to Annex 8 table 4 until the rod may be loaded; during curing of the injection mortar the temperature of the concrete must not fall below -5°C ;
- application of the torque moment given in Annex 3 table 1 using a calibrated torque wrench.

4.2.3. Responsibility of the manufacturer

It is the manufacturer's responsibility to ensure that the information on the specific conditions according to 1 and 2 including Annexes referred to in 4.2.1. and 4.2.2. is given to those who are concerned. This information may be made by reproduction of the respective parts of the European Technical Approval. In addition all installation data shall be shown clearly on the package and/or on an enclosed instruction sheet, preferably using illustration(s).

The minimum data required are:

- drill bit diameter,
- hole depth,
- diameter of anchor rod,
- minimum effective anchorage depth,
- information on the installation procedure, including cleaning of the hole with the cleaning equipments, preferably by means of an illustration,
- material and property class of metal parts acc. to Annex 5, Table 3,
- anchor component installation temperature,
- ambient temperature of the concrete during installation of the anchor,
- admissible processing time (open time) of the mortar,
- curing time until the anchor may be loaded as a function of the ambient temperature in the concrete during installation,
- maximum torque moment,
- identification of the manufacturing batch,

All data shall be presented in a clear and explicit form.

5 Recommendations concerning packaging, transport and storage.

The mortar cartridges shall be protected against sun radiation and shall be stored according to the manufacturer's installation instructions in dry conditions at temperatures of at least 5°C to not more than +25°C.

Mortar cartridges with expired shelf life must no longer be used.

The anchor shall only be packaged and supplied as a complete unit. Foil packs may be packed separately from metal parts.

**The original French version is
signed by**

**Le Directeur Technique
C. BALOCHE**

Injection mortar: hybrid system with resin, hardener and cement water component


Foil pack 330ml, 500ml

Marking:



CT 1
 Production time, -day, -line
 Expiration date



Static Mixer

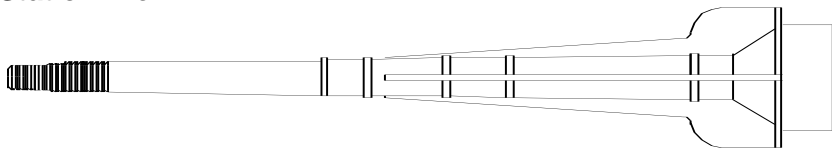

Steel elements:

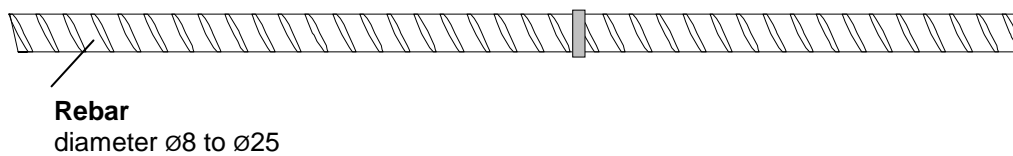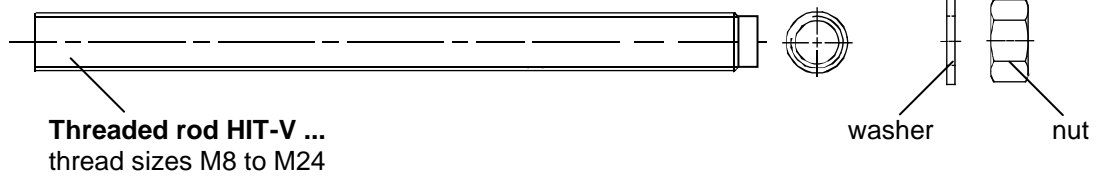



Injection System Hilti HIT-CT 1

Product and intended use

Annex 1

of European
 technical approval

ETA – 11/0354

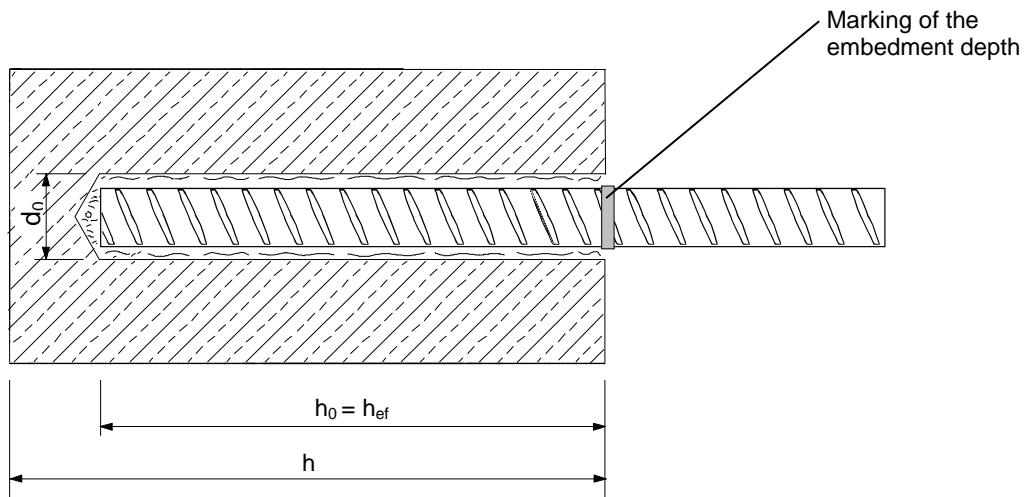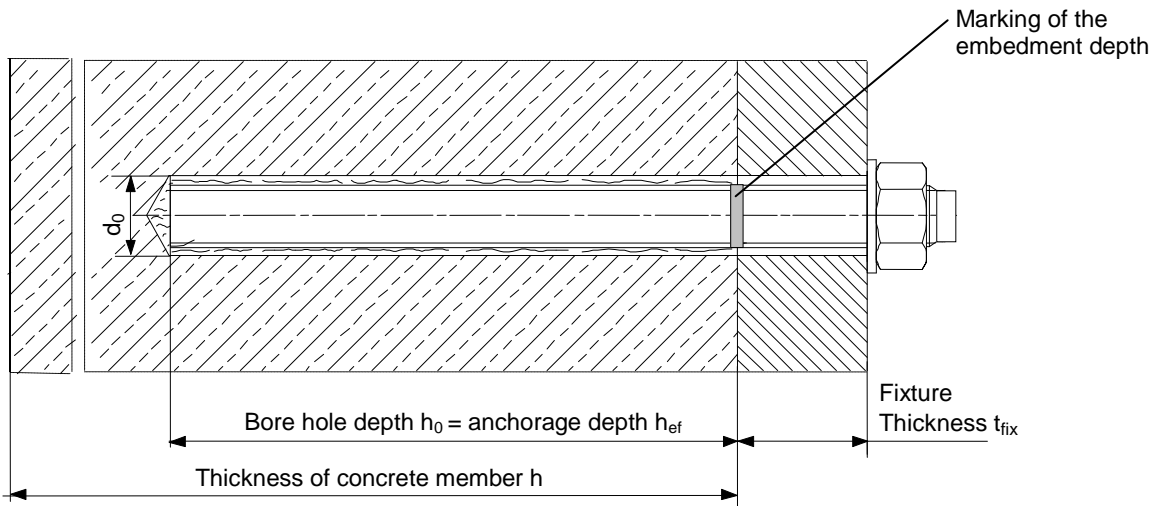

Use category: Installation in dry or water saturated concrete, (not in flooded holes)

Temperature range I: -40°C to +40°C (max long term temperature +24°C and max short term temperature +40°C)

Temperature range II: -40°C to +80°C (max long term temperature +50°C and max short term temperature +80°C)

Injection System Hilti HIT-CT 1

Installed anchor and intended use

Annex 2


of European technical approval

ETA – 11/0354

Table 1: Installation parameters of anchor rod HIT-V

HIT-CT 1 with HIT-V		M8	M10	M12	M16	M20	M24
Diameter of element	d [mm]	8	10	12	16	20	24
Range of anchorage depth h_{ef} and bore hole depth h_0 HIT-V-...	min [mm]	64	80	96	128	160	192
	max [mm]	96	120	144	192	240	288
Nominal diameter of drill bit	d_0 [mm]	10	12	14	18	22	28
Diameter of clearance hole in the fixture	$d_f \leq$ [mm]	9	12	14	18	22	26
Maximum torque moment	T_{max} [Nm]	10	20	40	80	150	200
Minimum thickness of concrete member	h_{min} [mm]	$h_{ef} + 30 \text{ mm}$ $\geq 100 \text{ mm}$			$h_{ef} + 2d_0$		
Minimum spacing	s_{min} [mm]	40	50	60	80	100	120
Minimum edge distance	c_{min} [mm]	40	50	60	80	100	120

HIT-V...

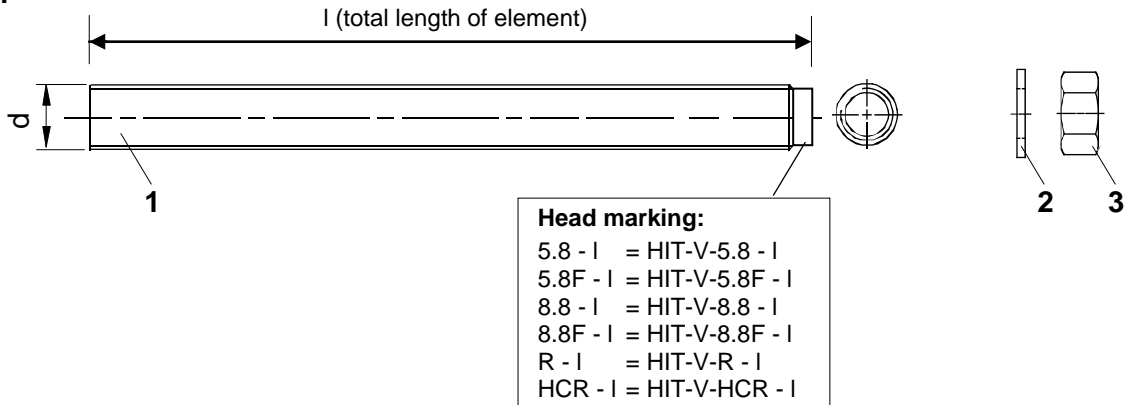

Injection System Hilti HIT-CT 1

**Installation parameter
 Threaded rod HIT-V**

Annex 3

of European
 technical approval


ETA - 11/0354

Table 2: Installation parameters of anchor element rebar

HIT-CT 1 with Rebar		Ø8	Ø10	Ø12	Ø14	Ø16	Ø20	Ø25
Diameter of element	d [mm]	8	10	12	14	16	20	25
Range of anchorage depth h_{ef} and bore hole depth h_0	min [mm]	64	80	96	112	128	160	200
	max [mm]	96	120	144	168	192	240	300
Nominal diameter of drill bit	d_0 [mm]	10/12 ¹⁾	12/14 ¹⁾	14/16 ¹⁾	18	20	25	32
Minimum thickness of concrete member	h_{min} [mm]	$h_{ef} + 30\text{mm}$ $\geq 100\text{ mm}$			$h_{ef} + 2d_0$			
Minimum spacing	s_{min} [mm]	40	50	60	70	80	100	125
Minimum edge distance	c_{min} [mm]	40	50	60	70	80	100	125

¹⁾ Both given values for drill bit diameter can be used.

Rebar

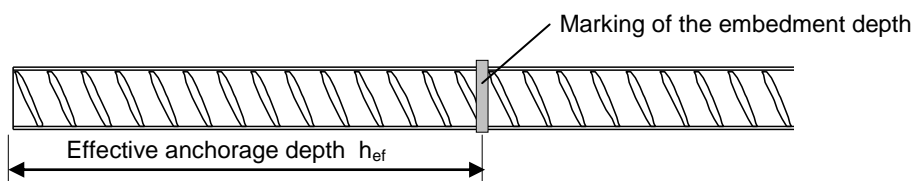

Refer to EN 1992-1-1 Annex C Table C.1 and C.2N, Properties of reinforcement:

Product form		Bars and de-coiled rods	
Class		B	C
Characteristic yield strength f_{yk} or $f_{0,2k}$ (MPa)		400 to 600	
Minimum value of $k = (f_t/f_y)_k$		$\geq 1,08$	$\geq 1,15$ < 1,35
Characteristic strain at maximum force, ϵ_{uk} (%)		$\geq 5,0$	$\geq 7,5$
Bendability		Bend/Rebend test	
Maximum deviation from nominal mass (individual bar) (%)	Nominal bar size (mm) ≤ 8	$\pm 6,0$	
	> 8	$\pm 4,5$	
Bond: Minimum relative rib area, $f_{R,min}$ (determination according to EN 15630)	Nominal bar size (mm) 8 to 12	0,040	
	> 12	0,056	

Height of the rebar rib h_{rib} :

The height of the rebar rib h_{rib} shall fulfil the following requirement: $0,05 \cdot d \leq h_{rib} \leq 0,07 \cdot d$
 with: d = nominal diameter of the rebar element

Injection System Hilti HIT-CT 1	Annex 4 of European technical approval ETA – 11/0354
Installation parameter Rebar	

Table 3: Materials

Designation	Material
Metal parts made of rebar	
Rebar	see Annex 4
Metal parts made of zinc coated steel	
threaded rod HIT-V-5.8(F)	strength class 5.8 EN ISO 898-1, A ₅ > 8% Ductile steel galvanized ≥ 5μm EN ISO 4042 (F) hot dipped galvanized ≥ 45μm EN ISO 10684
threaded rod HIT-V-8.8(F)	strength class 8.8 EN ISO 898-1, A ₅ > 8% Ductile steel galvanized ≥ 5μm EN ISO 4042 (F) hot dipped galvanized ≥ 45μm EN ISO 10684
washer ISO 7089	steel galvanized EN ISO 4042; hot dipped galvanized EN ISO 10684
nut EN ISO 4032	strength class 8 ISO 898-2 steel galvanized ≥ 5μm EN ISO 4042 hot dipped galvanized ≥ 45μm EN ISO 10684
Metal parts made of stainless steel	
threaded rod HIT-V-R	for ≤ M24: strength class 70 EN ISO 3506-1; A ₅ > 8% Ductile for > M24: strength class 50 EN ISO 3506-1; A ₅ > 8% Ductile stainless steel 1.4401; 1.4404; 1.4578; 1.4571; 1.4439; 1.4362 EN 10088
washer ISO 7089	stainless steel 1.4401; 1.4404; 1.4578; 1.4571; 1.4439; 1.4362 EN 10088
nut EN ISO 4032	strength class 70 EN ISO 3506-2 stainless steel 1.4401; 1.4404; 1.4578; 1.4571; 1.4439; 1.4362 EN 10088
Metal parts made of high corrosion resistant steel	
threaded rod HIT-V-HCR	for ≤ M20: R _m = 800 N/mm ² ; R _{p0,2} = 640 N/mm ² , A ₅ > 8% Ductile for > M20: R _m = 700 N/mm ² ; R _{p0,2} = 400 N/mm ² , A ₅ > 8% Ductile high corrosion resistant steel 1.4529, 1.4565 EN 10088
washer ISO 7089	high corrosion resistant steel 1.4529, 1.4565 EN 10088
nut EN ISO 4032	strength class 70 EN ISO 3506-2 high corrosion resistant steel 1.4529, 1.4565 EN 10088

Injection System Hilti HIT-CT 1

Materials


Annex 5

of European
technical approval


ETA – 11/0354

Instruction for use

Bore hole drilling

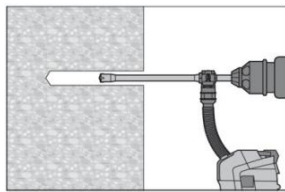


Drill hole to the required embedment depth with an appropriately sized Hilti TE-CD or TE-YD hollow drill bit with Hilti vacuum attachment. This drilling method properly cleans the borehole and removes dust while drilling. After drilling is complete, proceed to the "injection preparation" step in the instructions for use.

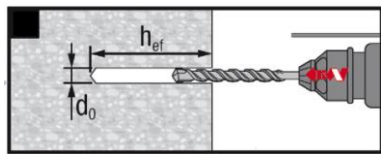


Drill hole to the required embedment depth with a hammer drill set in rotation-hammer mode using an appropriately sized carbide drill bit.

Bore hole cleaning Just before setting an anchor, the bore hole must be free of dust and debris.


a) Manual Cleaning (MC) for bore hole diameters $d_0 \leq 20\text{mm}$ and bore hole depth $h_0 \leq 10d_s$

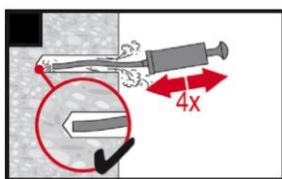

The Hilti manual pump may be used for blowing out bore holes up to diameters $d_0 \leq 20\text{ mm}$ and embedment depths up to $h_{ef} \leq 10d_s$. Blow out at least 4 times from the back of the bore hole until return air stream is free of noticeable dust.

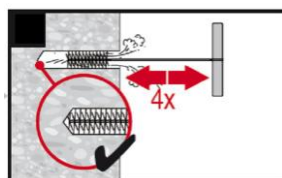


Brush 4 times with the specified brush size (brush $\varnothing \geq$ bore hole \varnothing , see Table 5) by inserting the steel brush Hilti HIT-RB to the back of the hole (if needed with extension) in a twisting motion and removing it. The brush must produce natural resistance as it enters the bore hole -- if not, the brush is too small and must be replaced with the proper brush diameter.

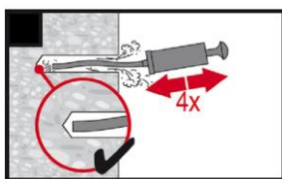


Blow out again with manual pump at least 4 times until return air stream is free of noticeable dust.


b) Compressed air cleaning (CAC) for all bore hole diameters d_0 and all bore hole depth h_0

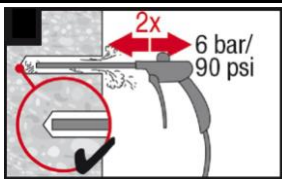

Blow 2 times from the back of the hole (if needed with nozzle extension) over the hole length with oil-free compressed air (min. 6 bar at $6\text{ m}^3/\text{h}$) until return air stream is free of noticeable dust.

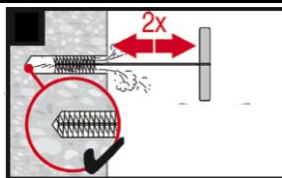

Brush 2 times with the specified brush size (brush $\varnothing \geq$ bore hole \varnothing , see Table 5) by inserting the steel brush Hilti HIT-RB to the back of the hole (if needed with extension) in a twisting motion and removing it. The brush must produce natural resistance as it enters the bore hole -- if not, the brush is too small and must be replaced with the proper brush diameter.

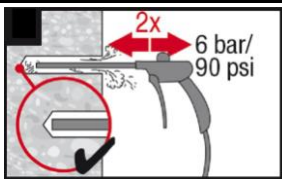

Blow again with compressed air 2 times until return air stream is free of noticeable dust.

Injection System Hilti HIT-CT 1


Annex 6

Installation instruction I

of European technical approval

ETA – 11/0354


Injection preparation

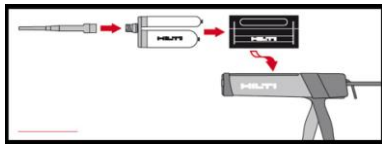

Tightly attach Hilti mixing nozzle to foil pack manifold. Do not modify the mixing nozzle.

Insert foil pack into the foil pack holder.
 Observe the Instruction for Use of the dispenser
 Check foil pack holder for proper function. Put foil pack into foil pack holder. Do not use damaged foil packs / holders.
 Insert foil pack holder with foil pack into dispenser.

Push release trigger, retract plunger and insert foil pack holder with foil pack into the appropriate Hilti dispenser.

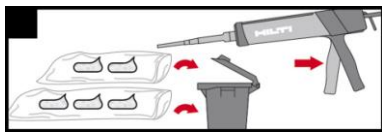


Discard initial adhesive. The foil pack opens automatically as dispensing is initiated. Depending on the size of the foil pack an initial amount of adhesive has to be discarded.

Discard quantities are 2 strokes for 330ml foil pack and 3 strokes for 500ml foil pack

Inject adhesive



Inject the adhesive starting at the back of the hole, slowly withdrawing the mixer with each trigger pull.

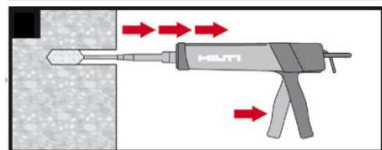


Fill holes approximately 2/3 full, or as required to ensure that the annular gap between the anchor and the concrete is completely filled with adhesive along the embedment length.




After injection is completed, depressurize the dispenser by pressing the release trigger. This will prevent further adhesive discharge from the mixer.

Inject adhesive - Overhead installation or installation with embedment depth $h_{ef} > 250\text{mm}$

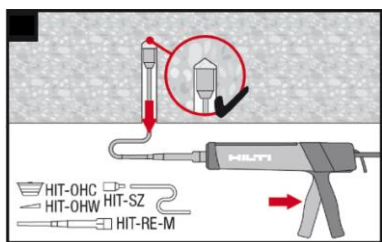

For overhead installation and installation with embedment depth $h_{ef} > 250\text{mm}$ the injection is only possible with the aid of extensions and piston plugs.

Assemble mixer, extension(s) and appropriately sized piston plug (see Table 5).

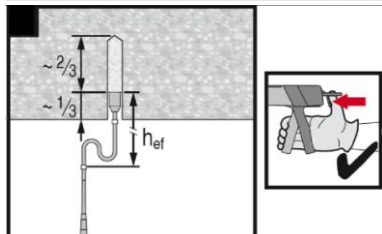

Insert piston plug to back of the hole and inject adhesive. During injection the piston plug will be naturally extruded out of the bore hole by the adhesive pressure.

Injection System Hilti HIT-CT 1




Annex 7

Installation Instruction II

of European technical approval

ETA – 11/0354

Setting the element

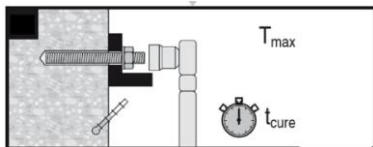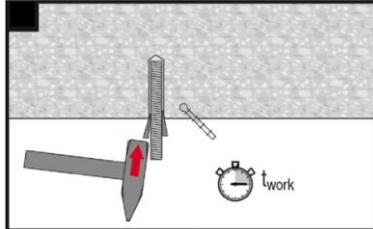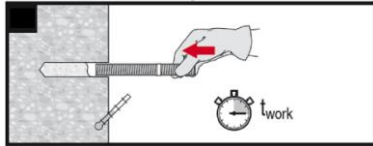

Before use, verify that the element is dry and free of oil and other contaminants.

Mark and set element to the required embedment depth till working time t_{work} has elapsed. The working time t_{work} is given in

Table 4.

For overhead installation use piston plugs and fix embedded parts with e.g. wedges.

Loading the anchor:

After required curing time t_{cure} (see Table 4) the anchor can be loaded. The applied installation torque shall not exceed the values T_{max} given in Table 1.

Table 4: Working time, curing time¹⁾

Base material temperature	Working time “ t_{work} ”	Curing time “ t_{cure} ”
$-5\text{ °C} \leq T_{base\ material} < 0\text{ °C}$	60 min	6 h
$0\text{ °C} \leq T_{base\ material} < 5\text{ °C}$	40 min	3 h
$5\text{ °C} \leq T_{base\ material} < 10\text{ °C}$	25 min	2 h
$10\text{ °C} \leq T_{base\ material} < 20\text{ °C}$	10 min	90 min
$20\text{ °C} \leq T_{base\ material} < 30\text{ °C}$	4 min	75 min
$30\text{ °C} \leq T_{base\ material} \leq 40\text{ °C}$	2 min	60 min

¹⁾ The curing time data are valid for dry anchorage base only.
 In water saturated anchorage base the curing times must be doubled.

Injection System Hilti HIT-CT 1







Installation Instruction III
Working time, curing time

Annex 8

of European
 technical approval

ETA – 11/0354

Table 5: Bore hole cleaning: Steel brush – Installation with Piston Plug

Element	Size	Nominal drill bit diameter d_0 [mm]		Steel brush	Piston plug	Cleaning methods	
		TE-C TE-Y	TE-CD TE-YD	HIT-RB	HIT-SZ	Manual cleaning (MC)	Compressed air cleaning (CAC)
						Manual cleaning (MC)	Compressed air cleaning (CAC)
	M8	10	-	HIT-RB 10	-	Yes ... $h_{ef} \leq 80\text{mm}$	Yes
	M10	12	12	HIT-RB 12	HIT-SZ 12	Yes ... $h_{ef} \leq 100\text{mm}$	Yes
	M12	14	14	HIT-RB 14	HIT-SZ 14	Yes ... $h_{ef} \leq 120\text{mm}$	Yes
	M16	18	18	HIT-RB 18	HIT-SZ 18	Yes ... $h_{ef} \leq 160\text{mm}$	Yes
	M20	22	22	HIT-RB 22	HIT-SZ 22	No	Yes
	M24	28	28	HIT-RB 28	HIT-SZ 28	No	Yes
	Ø8	10	12	HIT-RB 10	HIT-SZ 10	Yes ... $h_{ef} \leq 80\text{mm}$	Yes
		12 ¹⁾		HIT-RB 12	HIT-SZ 12		
	Ø10	12	14 ¹⁾	HIT-RB 12	HIT-SZ 12	Yes ... $h_{ef} \leq 100\text{mm}$	Yes
		14 ¹⁾		HIT-RB 14	HIT-SZ 14		
	Ø12	14	16 ¹⁾	HIT-RB 14	HIT-SZ 14	Yes ... $h_{ef} \leq 120\text{mm}$	Yes
		16 ¹⁾		HIT-RB 16	HIT-SZ 16		
	Ø14	18	18	HIT-RB 18	HIT-SZ 18	Yes ... $h_{ef} \leq 140\text{mm}$	Yes
Ø16	20	20	HIT-RB 20	HIT-SZ 20	Yes ... $h_{ef} \leq 160\text{mm}$	Yes	
Ø20	25	25	HIT-RB 25	HIT-SZ 25	No	Yes	
Ø25	32	32	HIT-RB 32	HIT-SZ 32	No	Yes	

¹⁾ Both given values for drill bit diameter can be used.

Automatic Cleaning (AC):

Cleaning is performed during drilling with Hilti TE-CD and TE-YD drilling system including vacuum cleaner.



Manual Cleaning (MC):

Hilti hand pump recommended for blowing out bore holes with diameters $d_0 \leq 20\text{mm}$ and bore hole depth $h_0 \leq 10d_s$.



Compressed air cleaning (CAC):

Air nozzle with an orifice opening of minimum 3,5 mm in diameter recommended for blowing out with compressed air (min. 6 bar at 6 m³/h).



Injection System Hilti HIT-CT 1

**Bore hole cleaning
 Installation with piston plug**


Annex 9

of European
 technical approval

ETA – 11/0354

Table 6: Design method A, Characteristic tension load values

HIT-CT 1 with HIT-V...			M8	M10	M12	M16	M20	M24	
Steel failure HIT-V...									
Characteristic resistance HIT-V-5.8(F)	$N_{Rk,s}$	[kN]	18	29	42	79	123	177	
Characteristic resistance HIT-V-8.8(F)	$N_{Rk,s}$	[kN]	29	46	67	126	196	282	
Partial safety factor	$\gamma_{Ms,N}^{1)}$	[-]	1,5						
Characteristic resistance HIT-V-R	$N_{Rk,s}$	[kN]	26	41	59	110	172	247	
Partial safety factor	$\gamma_{Ms,N}^{1)}$	[-]	1,87						
Characteristic resistance HIT-V-HCR	$N_{Rk,s}$	[kN]	29	46	67	126	196	247	
Partial safety factor	$\gamma_{Ms,N}^{1)}$	[-]	1,5						
Combined Pull-out and Concrete cone failure ²⁾									
Diameter of threaded rod	d	[mm]	8	10	12	16	20	24	
Characteristic bond resistance in non-cracked concrete C20/25									
Temperature range I ³⁾ :	40°C/24°C	τ_{Rk}	[N/mm ²]	12	11	11	10	9,5	9,0
Temperature range II ³⁾ :	80°C/50°C	τ_{Rk}	[N/mm ²]	11	11	10	9,5	9,0	8,5
Increasing factor for $\tau_{Rk,p}$ in non cracked concrete	C30/37	1,06							
	C40/50	1,11							
	C50/60	1,14							
Splitting failure ²⁾									
Edge distance $c_{cr,sp}$ [mm] for	$h / h_{ef}^{4)} \geq 2,0$	1,0 h_{ef}							
	$2,0 > h / h_{ef}^{4)} > 1,3$	4,6 h_{ef} - 1,8 h							
	$h / h_{ef}^{4)} \leq 1,3$	2,26 h_{ef}							
Spacing	$s_{cr,sp}$	[mm]	2 $c_{cr,sp}$						
Partial safety factor	$\gamma_{Mp} = \gamma_{Mc} = \gamma_{Msp}^{1)}$	[-]	1,8 ⁵⁾	1,8 ⁵⁾	1,8 ⁵⁾	1,8 ⁵⁾	1,8 ⁵⁾	1,8 ⁵⁾	

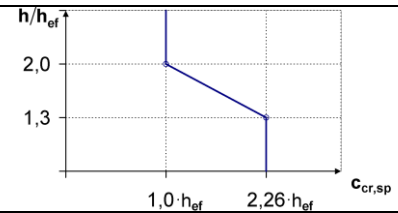

- 1) In absence of national regulations
- 2) Calculation of concrete failure and splitting see chapter 4.2.1.
- 3) Explanation see chapter 1.2
- 4) h ... concrete member thickness, h_{ef} ... effective anchorage depth
- 5) The partial safety factor $\gamma_2 = 1,2$ is included.

Injection System Hilti HIT-CT 1

**Characteristic tension load values
 Threaded rods HIT-V**

Annex 10

of European
 technical approval

ETA – 11/0354

Table 7: Displacements under tension load ¹⁾

HIT-CT 1 with HIT-V			M8	M10	M12	M16	M20	M24
Temperature range I ²⁾: 40°C / 24°C								
Displacement	δ_{N0}	[mm/(N/mm ²)]	0,06	0,06	0,06	0,07	0,07	0,07
Displacement	$\delta_{N\infty}$	[mm/(N/mm ²)]	0,07	0,07	0,07	0,08	0,08	0,08
Temperature range II ²⁾: 80°C / 50°C								
Displacement	δ_{N0}	[mm/(N/mm ²)]	0,06	0,06	0,06	0,07	0,07	0,07
Displacement	$\delta_{N\infty}$	[mm/(N/mm ²)]	0,07	0,07	0,07	0,08	0,08	0,08

¹⁾ Calculation of displacement under service load: τ_{Sd} design value of bond stress

Displacement under short term loading = $\delta_{N0} \cdot \tau_{Sd}/1,4$

Displacement under long term loading = $\delta_{N\infty} \cdot \tau_{Sd}/1,4$

²⁾ Explanation see chapter 1.2

Injection System Hilti HIT-CT 1

**Displacements under tension load
for threaded rods HIT-V...**

Annex 11

of European
technical approval

ETA – 11/0354

Table 8: Design method A, Characteristic shear load values

HIT-CT 1 with HIT-V			M 8	M 10	M 12	M 16	M 20	M 24
Steel failure¹⁾ without lever arm								
Characteristic resistance HIT-V-5.8(F)	$V_{Rk,s}$ [kN]		9	15	21	39	61	88
Characteristic resistance HIT-V-8.8(F)	$V_{Rk,s}$ [kN]		15	23	34	63	98	141
Characteristic resistance HIT-V-R	$V_{Rk,s}$ [kN]		13	20	30	55	86	124
Characteristic resistance HIT-V-HCR	$V_{Rk,s}$ [kN]		15	23	34	63	98	124
Steel failure¹⁾ with lever arm								
Characteristic resistance HIT-V-5.8(F)	$M^0_{Rk,s}$ [Nm]		19	37	66	167	325	561
Characteristic resistance HIT-V-8.8(F)	$M^0_{Rk,s}$ [Nm]		30	60	105	266	519	898
Characteristic resistance HIT-V-R	$M^0_{Rk,s}$ [Nm]		26	52	92	233	454	786
Characteristic resistance HIT-V-HCR	$M^0_{Rk,s}$ [Nm]		30	60	105	266	520	786
Partial safety factor steel failure								
HIT-V grade 5.8 or 8.8	$\gamma_{Ms,V}^{2)}$ [-]		1,25					
HIT-V-R	$\gamma_{Ms,V}^{2)}$ [-]		1,56					
HIT-V-HCR	$\gamma_{Ms,V}^{2)}$ [-]		1,25					1,75
Concrete pryout failure								
Factor in equation (5.7) of Technical Report TR 029 for the design of bonded anchors	k [-]		2,0					
Partial safety factor	$\gamma_{Mcp}^{2)}$ [-]		1,5 ³⁾					
Concrete edge failure⁴⁾								
Partial safety factor	$\gamma_{Mc}^{2)}$ [-]		1,5 ³⁾					

- 1) Acc. chapter 4.2.2. commercial standard rods that fulfill the ductility requirement $A_s > 8\%$ (see Table 3) can be used only.
 2) In absence of national regulations.
 3) The partial safety factor $\gamma_2 = 1,0$ is included.
 4) Concrete edge failure see chapter 5.2.3.4 of Technical Report TR 029.

Table 9: Displacement under shear load¹⁾

HIT-CT 1 with HIT-V			M8	M10	M12	M16	M20	M24
Displacement	δ_{V0} [mm/kN]		0,06	0,06	0,05	0,04	0,04	0,03
Displacement	$\delta_{V\infty}$ [mm/kN]		0,09	0,08	0,08	0,06	0,06	0,05

- 1) Calculation of displacement under service load: V_{Sd} design value of shear load
 Displacement under short term loading = $\delta_{V0} \cdot V_{Sd}/1,4$
 Displacement under long term loading = $\delta_{V\infty} \cdot V_{Sd}/1,4$

Injection System Hilti HIT-CT 1


**Characteristic shear load values
and displacements under shear load
Threaded rods HIT-V**

Annex 12

of European
technical approval
ETA – 11/0354

Table 10: Design method A, Characteristic tension load values

HIT-CT 1 with rebar			Ø8	Ø10	Ø12	Ø14	Ø16	Ø20	Ø25	
Steel failure rebar										
Characteristic resistance for rebar BSt 500 S acc. to DIN 488 ¹⁾	$N_{Rk,s}$	[kN]	28	43	62	85	111	173	270	
Partial safety factor for rebar BSt 500 S acc. to DIN 488 ²⁾	$\gamma_{Ms,N}$ ³⁾	[-]	1,4							
Combined Pull-out and Concrete cone failure⁴⁾										
Diameter of threaded rod	d	[mm]	8	10	12	14	16	20	25	
Characteristic bond resistance in non-cracked concrete C20/25										
Temperature range I ⁵⁾ :	40°C/24°C	τ_{Rk}	[N/mm ²]	7,0	7,5	7,5	7,5	7,5	8,0	8,0
Temperature range II ⁵⁾ :	80°C/50°C	τ_{Rk}	[N/mm ²]	7,0	7,0	7,0	7,0	7,0	7,5	7,5
Increasing factor for $\tau_{Rk,p}$ in non cracked concrete	C30/37	1,06								
	C40/50	1,11								
	C50/60	1,14								
Splitting failure⁴⁾										
Edge distance $c_{cr,sp}$ [mm] for	$h / h_{ef}^{6)} \geq 2,0$	1,0 h_{ef}								
	$2,0 > h / h_{ef}^{6)} > 1,3$	4,6 h_{ef} - 1,8 h								
	$h / h_{ef}^{6)} \leq 1,3$	2,26 h_{ef}								
Spacing	$s_{cr,sp}$	[mm]	2 $c_{cr,sp}$							
Partial safety factor	$\gamma_{Mp} = \gamma_{Mc} = \gamma_{Msp}$ ³⁾	[-]	1,8 ⁷⁾	1,8 ⁷⁾	1,8 ⁷⁾	1,8 ⁷⁾	1,8 ⁷⁾	1,8 ⁷⁾	1,8 ⁷⁾	

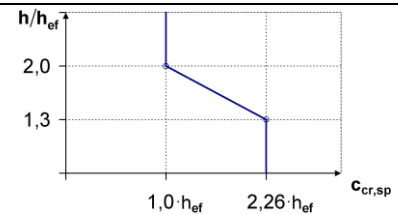

- 1) The characteristic tension resistance $N_{Rk,s}$ for rebars that do not fulfil the requirements acc. DIN 488 shall be calculated acc. Technical Report TR029, Equation (5.1).
- 2) The partial safety factor $\gamma_{Ms,N}$ for rebars that do not fulfil the requirements acc. DIN 488 shall be calculated acc. Technical Report TR029, Equation (3.3a).
- 3) In absence of national regulations
- 4) Calculation of concrete failure and splitting see chapter 4.2.1
- 5) Explanation see chapter 1.2
- 6) h ... concrete member thickness, h_{ef} ... effective anchorage depth
- 7) The partial safety factor $\gamma_2 = 1,2$ is included.

Table 11: Displacements under tension load¹⁾

HIT-CT 1 with rebar			Ø8	Ø10	Ø12	Ø14	Ø16	Ø20	Ø25
Temperature range I²⁾: 40°C / 24°C									
Displacement	δ_{N0}	[mm/(N/mm ²)]	0,06	0,06	0,06	0,07	0,07	0,07	0,07
Displacement	$\delta_{N\infty}$	[mm/(N/mm ²)]	0,07	0,07	0,07	0,08	0,08	0,08	0,08
Temperature range II²⁾: 80°C / 50°C									
Displacement	δ_{N0}	[mm/(N/mm ²)]	0,06	0,05	0,05	0,04	0,04	0,04	0,03
Displacement	$\delta_{N\infty}$	[mm/(N/mm ²)]	0,09	0,08	0,07	0,06	0,06	0,05	0,05

- 1) Calculation of displacement under service load: τ_{Sd} design value of bond stress
 Displacement under short term loading = $\delta_{N0} \cdot \tau_{Sd}/1,4$
 Displacement under long term loading = $\delta_{N\infty} \cdot \tau_{Sd}/1,4$
- 2) Explanation see chapter 1.2

Regarding design of post-installed rebar as anchor see chapter 4.2.1

Injection System Hilti HIT-CT 1	Annex 13 of European technical approval ETA – 11/0354
Characteristic values and displacement for tension load Rebar	

Table 12: Design method A, Characteristic shear load values

HIT-CT 1 with rebar			Ø8	Ø10	Ø12	Ø14	Ø16	Ø20	Ø25
Steel failure without lever arm									
Characteristic shear resistance for rebar BSt 500 S acc. to DIN 488 ¹⁾	$V_{Rk,s}$	[kN]	14	22	31	42	55	86	135
Partial safety factor for rebar BSt 500 S acc. to DIN 488 ²⁾	$\gamma_{Ms,V}$ ³⁾	[-]	1,5						
Steel failure with lever arm									
Characteristic shear resistance for rebar BSt 500 S acc. to DIN 488 ⁴⁾	$M^0_{Rk,s}$	[Nm]	33	65	112	178	265	518	1012
Partial safety factor for rebar BSt 500 S acc. to DIN 488 ²⁾	$\gamma_{Ms,V}$ ³⁾	[-]	1,5						
Concrete pryout failure									
Factor in equation (5.7) of Technical Report TR 029 for the design of bonded anchors	k	[-]	2,0						
Partial safety factor	γ_{Mcp} ³⁾	[-]	1,5 ⁵⁾						
Concrete edge failure⁶⁾									
Partial safety factor	γ_{Mc} ³⁾	[-]	1,5 ⁵⁾						

- 1) The characteristic shear resistance $V_{Rk,s}$ for rebars that do not fulfil the requirements acc. DIN 488 shall be calculated acc. Technical Report TR029, Equation (5.6).
- 2) The partial safety factor $\gamma_{Ms,V}$ for rebars that do not fulfil the requirements acc. DIN 488 shall be calculated acc. Technical Report TR029, Equation (3.3b).or (3.3c)..
- 3) In absence of national regulations
- 4) The characteristic bending resistance $M^0_{Rk,s}$ for rebars that do not fulfil the requirements acc. DIN 488 shall be calculated acc. Technical Report TR029, Equation (5.6b).
- 5) The partial safety factor $\gamma_2 = 1,0$ is included.
- 6) Concrete edge failure see chapter 5.2.3.4 of Technical Report TR 029.

Table 13: Displacements under shear load¹⁾

HIT-CT 1 with rebar			Ø8	Ø10	Ø12	Ø14	Ø16	Ø20	Ø25
Displacement	δ_{V0}	[mm/kN]	0,09	0,07	0,06	0,05	0,05	0,04	0,03
Displacement	$\delta_{V\infty}$	[mm/kN]	0,14	0,11	0,09	0,08	0,07	0,06	0,05

- 1) Calculation of displacement under service load: V_{Sd} design value of shear load
 Displacement under short term loading = $\delta_{S_{N0}} \cdot V_{Sd}/1,4$
 Displacement under long term loading = $\delta_{V\infty} \cdot V_{Sd}/1,4$

Regarding design of post-installed rebar as anchor see chapter 4.2.1

Injection System Hilti HIT-CT 1	Annex 14 of European technical approval ETA – 11/0354
Characteristic values and displacement for shear load Rebar	